

EXPERIMENTATION OF HYBRID METAL MATRIX OF ALLUMINIUM WITH BORON CARBIDE AND GRAPHITE AND ANALYSIS WITH DESTRUCTIVE TESTS & MICROSTRUCTURE

DR.S.VENUGOPAL¹, V.S.VINOTHKUMAR², VIGIDHARA³

¹*Professor, Department of Mechanical Engineering*

²*Assistant Professor, Department of Mechanical Engineering*

³*Assistant Professor, Department of Aeronautical Engineering*

Dhanalakshmi Srinivasan College of Engineering and Technology, Mamallapuram

ABSTRACT;

The importance of reinforced particle with aluminium metal matrix is to study and predict in the enhancement of mechanical properties like tensile and tribological property. Metal matrix composites (MMCs) constitute an important class of design and weight-efficient structural materials that are encouraging every sphere of engineering applications. There has been an increasing interest in composites containing low density and low cost reinforcements. With the increasing demand of light-weight materials in the emerging industrial applications, fabrication of aluminium-boron carbide with graphite composites is required. In this context aluminium - boron carbide with graphite composites were fabricated by stir casting with different particulate composition of B₄C (5%,10%). Microstructure analysis was done with scanning electron microscope. With the increase the amount of the boron carbide, the density of the composites decreased whereas the hardness is increased. The ultimate compressive strength of the composites was increased with increase in the weight percentage of the boron carbide in the composites.

Keywords: Aluminium alloy, Boron carbide, graphite, stir casting, SEM, Mechanical properties.

INTRODUCTION;

Metal Matrix Composites (MMCs) have emerged as an important class of materials and are increasingly utilized in various engineering applications, such as aerospace, marine, automobile and turbine compressor engineering, which require materials offering a combination of light weight with considerably accelerated mechanical and physical properties such as strength, toughness, stiffness and resistance to high temperature.

Aluminum is the most frequently use matrix material due to its low density. Because of its extreme hardness and temperature resistant properties, B₄C, graphite are often used as reinforcement

within the aluminum matrix. This type of composite is more frequently used in the automotive industry today, particularly in various engine components as well as brakes and rotors.

Boron Carbide (B₄C) has many attractive properties, such as low specific gravity, high hardness value, high elastic modulus value and neutron absorption, which help B₄C to be widely used as armor materials. From limited information of B₄C reinforced aluminum matrix composites, there are several research works mainly focused on the wettability and chemical reaction between aluminum and boron carbide with graphite. This paper aims to analyze the microstructure evolution of B₄C/Al composites during mechanical alloying bonding with graphite and the microstructure, mechanical property of the composites prepared by stir casting.

LITERATURE REVIEW;

K. Madheswaran, S.Sugumar: has studied mechanical characterization of aluminium-boron carbide composites with influence of calcium carbide particles. The objective of this work is to fabricate and testing the mechanical properties of aluminium metal matrix composites with boron carbide and calcium carbide reinforcements at different volume fractions. Mechanical properties like tensile strength, shear strength and toughness of newly developed MMCs is improved significantly by incorporating boron carbide and calcium carbide particles. The toughness of material is considerably reduced if the percentage of calcium carbide addition is increases. From this study, it is concluded that the ultimate tensile strength of aluminium metal matrix composite with 2% of calcium carbide and 8% boron carbide reinforcements compared with 1% calcium carbide and 9% boron carbide reinforcements is increased by 8%.

Ehsan Ghasali, Masoud Alizadeh : Has worked on investigation of microstructure and mechanical properties of B₄C-Aluminium matrix composites prepared by microwave sintering. B₄C reinforced Aluminium composites were fabricated by microwave heating of the mixture of B₄C (10, 15 and 20 wt. %) and aluminium powder at 650, 750, 850 and 950°C. The effect of different amounts of B₄C on the microstructure and mechanical properties of aluminium matrix was examined. The maximum bending (238MPa) and compressive strength (330MPa) values were measured for composites sintered at 950 and 750°C respectively. The maximum hardness (112 Vickers) was measured for Al-20wt. % B₄C composite sintered at 850°C.

Experimental Details

2.1 Materials

Metal matrix composites containing 5 and 10 weight percentages of B₄C and 4 weight percentages of graphite particles were produced by liquid metallurgy route. For the production of MMCs, an Al LM25 alloy was used as the matrix material while B₄C, graphite particles with an average size of 80-90µm were used as the reinforcements. Al LM25 alloy having chemical composition as per the ASTM ingot specification is given below

2.2 Preparation of composites

In stir casting method before the casting reinforcements, stirrer, permanent mould preheated to 300⁰C to remove moisture and gases from the surface of the reinforcements, and equipment’s before casting. Now the required amount of Al LM25 is weighed and placed in the graphite crucible and heated to 730⁰C using resistance furnace then the degassing tablet is added to minimize the coating film defects by expelling the volatile components present in the melt during casting. The tablet helps in the removal of entrapped air in the melt and thus prevents casting defects like porosity and blow holes. Then the matrix Al LM25 is reinforced with B4C particulates with different weight percentages (5&10).

Cu	Mg	Si	Fe	Mn	Ni	Zn	Pb	Ti	Al
0.1 ma x	0.2- 0.6	6.5 - 7.5	0.5 ma x	0.3 max	0.1 max	0.1 m ax	0.1 max	0.2 m ax	Bal

Table 1Chemical composition of the matrix alloy Aluminum (LM25)

The micro particle of B₄C, Graphitewas added at the temperature of 710⁰C and constant rigorous stirring was done for 15mins until a clear vortex is formed.The melt was then superheated above the liquidstemperture and finally poured into a cast iron permanent mould to obtain cylindricalsamples of 15 mm diameter and 75 mm length. Unreinforced matrix alloy specimens were also cast for comparison purpose.

III. Testing of Composites

Micro Structure Analysis.Micro structural characterization studies were conducted on unreinforced and reinforced samples. This is accomplished by using scanning electron microscope. The compositesampleswere metallographically polished prior to examination. Characterization is done in etched conditions. Etching was accomplished using Keller’s reagent. The MM micrographs of composite and wear debris were obtained using the metallurgical microscope –Dewinter Tech. The images were taken in both secondary electron (SE) and back scattered electron (BSE) mode according to requirement.

Particle Size Analysis.Particle size of the milled powder was measured by Malvern particle size analyzer (Model Micro-P, range 0.05- 550 micron). Firstly, the liquid dispersant containing 500 ml of distilled water was kept in the sample holder. Then the 15 instrument was run keeping ultrasonic displacement at 10.00 micron and pump speed 1800 rpm. Electrolytic Etchant:1%HF

Tensile TestTensile tests were conducted at room temperature using a universal testing machine (UTM) in accordance with ASTM standard. The tensile test specimens of diameter 9mm and gauge length 45mm were machined from the cast composites with the gauge length of the specimens parallel to the longitudinal axis of the castings. For each composite, two tensile test specimens were tested and the average values of the ultimate tensile strength and yield strength were measured.

Wear Resistance Test.The wear resistance test is conducted on wear test machine in accordance with ASTM. The wear test specimens of diameter 15mm and gauge length 50mm were machined from the cast composites. For every composite, one wear resistance test specimens were tested. The wear resistance values of the samples were measured on the machined samples with a load of 1000gms, 40 RPM and 60 grade coarser abrasive sheet.

IV. RESULTS AND DISCUSSION;

It is well known stir casting process, the following figures show the distribution of aluminium- boron carbide with graphite particles through in metal matrix composite. The result indicates the reinforcement of particles as distributed in good manner the bonding between aluminium- boron carbide with graphite achieved through stir casting method. Addition of graphite added with aluminium, increases the ultimate tensile strength and wear resistance, reduce the coefficient of friction.

Micro Structure Of Al-B₄C With Addition Of Graphite

91% of Al and 5% of B₄C, 4% of Graphite

B₄C-Al with graphite showing different microstructures obtained after initially subsequently cooled in the furnace for 24 h (initial composition: 5 % B₄C-91% Al, 4% graphite), then obtaining the microstructure shows figure


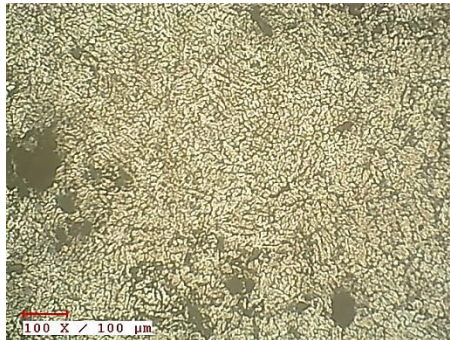


Figure 1 91% of Al and 5% of B₄C, 4% of Graphite

.86% of Al and 10% of B₄C, 4% of Graphite

B₄C-Al with graphite showing different microstructures obtained after initially heating to 700°C for one and half hour and subsequently cooled in the furnace for 24 h (initial composition: 10% B₄C-86% Al, 4% graphite), then obtaining the microstructure shows figure.

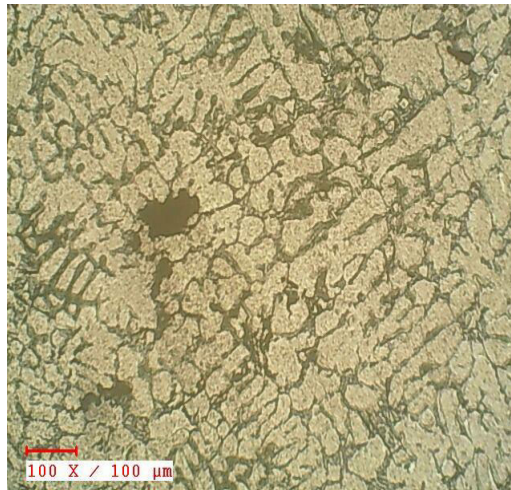

TENSILE TEST

we can see that the tensile strength was increased in the composites and have comparable variation. Weak interfacial bonds may result in decrease in tensile strength of the composite, but here the increase of tensile strength shows that there was good interfacial strength. From this result we can expect good interfacial strength when we heat the reinforcements at higher temperatures which will facilitate uniform distribution of more amount of composite without losing the strength.

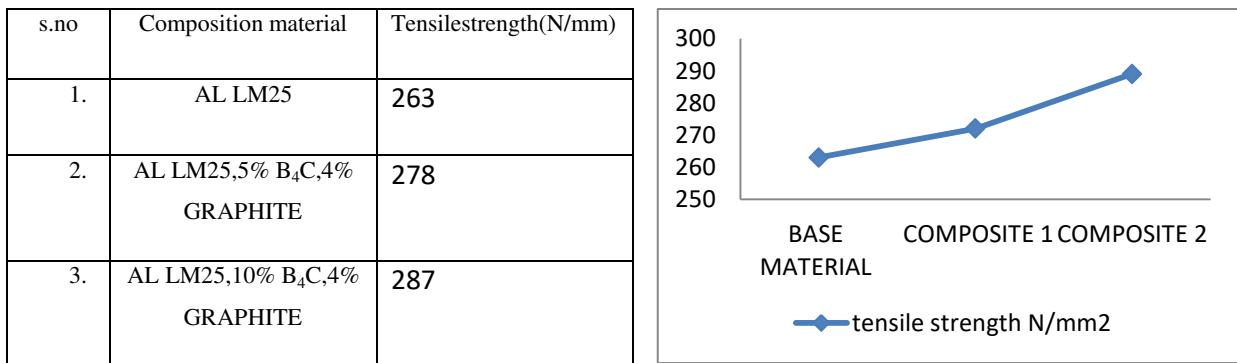


Figure 2 86% of Al and 10% of B₄C,4% of Graphite


Comparison of Tensile Strength

The microstructure shows network of interdentric Al-Si Eutectic particle in the matrix of Al solid solution. In this matrix, some porosity also observed

Wear test

When the friction is the predominant factor causing deterioration of materials, abrasion and wear testing will give data to compare materials or coatings and can help you predict of life time of material or coating.

s.no	Composition material	Wear loss
1.	AL LM25	0.20
2.	AL LM25,5% B ₄ C,4% GRAPHITE	0.15
3.	AL LM25,10% B ₄ C,4% GRAPHITE	0.17

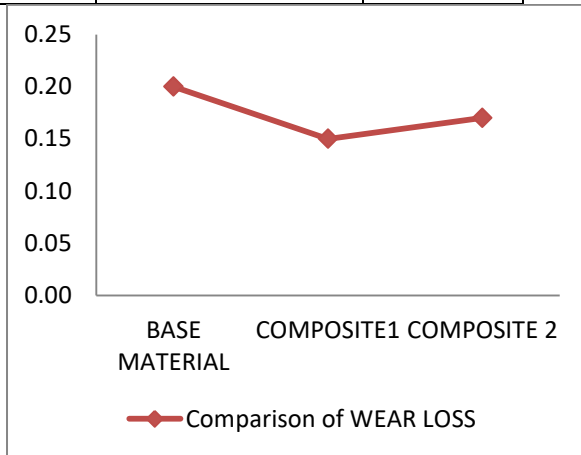

CONCLUSION;

The Al–B₄C–Gr hybrid composites were prepared successfully by stir casting method and reinforcement of boron carbide increased the strength of composites. Optimal per cent reinforcement can be of 12% for any value of sliding distance, speed and load within the range considered in this investigation. Al–B₄C–Gr hybrid composites are better substitutes the Al alloy owing to improved hardness and wear resistance as a result of the addition B₄C–Gr particulates to Al. Analysis shows that, increase in per cent reinforcement reduces the wear up to 12%.The hardness of the composites increased and density was decreased with increasing the amount of the boron carbide in the matrix phase. Increasing the amount of boron carbide particles in composites caused the ultimate compression strength to increase

REFERENCES;

1. **M.K. Surappa, P.K. Rohatgi**, Preparation and properties of cast aluminium-ceramic particle composites, *Journal of materials science*, 16(1981), p 983-993.
2. **J.W. Kaczmar, K. Pietrzak, W. Wlosinski**, The production and application of metal matrix composite materials, *Journal of material processing technology*, 106(2000), p 106:58-67.
3. **R.M. Mohanty, K. Balasubramanian, S.K. Seshadri**, Boron carbide-reinforced aluminium 1100 matrix composites: fabrication and properties, *Materials science and engineering*, 498(2008), p 42-52.
4. **K.H.W. Seah, J. Hemanth, S.C. Sharma**, Mechanical properties of aluminium/quartz particulate composites cast using metallic and non metallic chills, *Materials and design*, 24(2003), p 87-93.

5. **M.A. Belger, P.K. Rohatgi, N. Gupta**, Aluminium composite casting incorporating used and virgin foundry sand as particle reinforcements, solidification processing of metal matrix composites-Rohatgi honorary symposium, TMS Annual Meeting (2006), p 95-104
6. **S. Sulaiman, M. Sayuti, R. Samin**, Mechanical properties of the as cast quartz particulate reinforced LM6 alloy matrix composites, Journal of materials processing technology, 201(2008), p 731-735.
7. M.A. Belger, P.K Rohatgi, N. Gupta, *Aluminium composite casting incorporating used and virgin foundry sand as particle reinforcements, solidification processing of metal matrix composites*-Rohatgi honorary symposium, TMS Annual Meeting (2006), p 95-104
8. 2. S. Sulaiman, M. Sayuti, R. Samin, *Mechanical properties of the as cast quartz particulate reinforced LM6 alloy matrix composites*, Journal of materials processing technology, 201(2008), p 731-735.
9. T.R. Chapman, D.E. Niesz, R.T. Fox, T. Fawcett, *Wear-resistant aluminium-boron-carbide cermets for automotive brake applications*, Wear,236(1999),p81-87.
10. W.R. Blumenthal, G.T. Gray, T.N. Claytor, *Response of aluminium-infiltrated boron carbide cermets to shock wave loading*, Journal of material science, 29/17(1994), p 44567-4567